

R.H. Ottewill  
A.B. Schofield  
J.A. Waters

## Preparation of composite Latex particles by engulfment

Received: 7 January 1996  
Accepted: 8 January 1996

Prof. Dr. R.H. Ottewill (✉)  
A.B. Schofield J.A. Waters  
School of Chemistry  
University of Bristol  
Bristol BS8 1TS, United Kingdom

**Abstract** It can be predicted that, provided the interfacial energies are well chosen for two individual particles, then it is possible to engulf one particle into the other. This has now been achieved experimentally using poly-[butylmethacrylate] particles as the host material and poly-[styrene] particles for engulfment. Initially, anionic poly-[styrene] particles were heterocoagulated onto

electrosterically stabilised cationic particles of poly-[butylmethacrylate]. Then on heating the heterocoagulated units above the glass transition temperature of the latter engulfment occurred.

**Key words** Engulfment – interfacial energy – heterocoagulation – Poly-[styrene] – Poly-[butylmethacrylate]

### Introduction

The possibility of preparing polymer colloid particles with a well-defined morphology such as a core-shell with one polymer as the core and another as the shell is of considerable interest both from a fundamental point of view and from the standpoint of technological applications. Although considerable work has been reported on the preparation of particles using mixed monomers and with seeded polymerisation using a second monomer the outcome from these approaches has not always been predictable and many particle morphologies have been described [1–18]. However, recently a number of publications have appeared suggesting theories, based on the surface energies of the polymers, which enable the identification of the energetically favoured morphologies for composite particles [19–26]. These considerations suggested the possibility of preparing composite polymer particles by a process in which dissimilar preformed particles are induced to heterocoagulate. Then rearrangement of the composite, promoted by a reduction of the total interfacial energy, proceeds with one particle type spreading around or “engulfing” a particle of the other type when the temperature

is raised above the engulfing polymer glass transition [23,25].

In one of the earlier experiments [24], random copolymer particles composed of poly-(methyl methacrylate), PMMA, and poly-(butyl acrylate), PBA, were used as the engulfing particles. These were prepared by emulsion polymerisation, using ammonium persulphate as the initiator and also using methoxy-polyethylene glycol methacrylate, to incorporate PEG chains of ca. 2000 molecular weight on to the surface to act as a steric stabiliser [24]; these has a number-average diameter of 670 nm. A latex of PBA with a number-average diameter of 95nm was also produced by emulsion polymerisation using ammonium persulphate and constituted the smaller particles which were to be engulfed.

In order to prepare composite particles the PMMA/PBA copolymer particles were placed in a stirred container and the temperature raised to 65°C. The smaller PBA particles and a 0.01mol dm<sup>-3</sup> solution of dodecyl trimethyl ammonium bromide were then added simultaneously but separately through different tubes over a period of 1.5 hours. The resultant particles, containing engulfed PBA, has a final diameter of 780nm as determined by disc centrifuge photosedimentometry [24].

Several methods can be used to induce the necessary heterocoagulation. In the present work the dissimilar particles were prepared with opposite electrical charges at their surfaces. Cationic particles of poly-(butyl methacrylate), PBMA, prepared using a cationic initiator, were used as the host particles; these particles were, in addition, also sterically stabilised by the incorporation of MeOPEGMA chains onto the surface. The particles to be engulfed were poly-(styrene), PS, prepared by an emulsion polymerisation technique using ammonium persulphate. The engulfment process was carried out at 70°C, which was 35°C above the glass-transition temperature of PBMA.

### Theory

The conditions for engulfment based on surface energy considerations have been discussed previously [23-26] but a short summary is given here to provide continuity. Initially, on the basis of two separated particles, as shown in Fig.1, we can write that the total surface energy for one host particle of radius  $R_H$  and one core particle of radius  $R_C$  is given by:

$$E_{SEP} = 4\pi R_H^2 \gamma_{HW} + 4\pi R_C^2 \gamma_{CW} \quad ,$$

where  $\gamma_{HW}$  and  $\gamma_{CW}$  are respectively the surface energies of the host particles and the core particles in water. Alternatively, in terms of the volumes of the separated particles the equation can be written as,

$$E_{SEP}/4\pi(3/4\pi)^{2/3} = V_H^{2/3} \gamma_{HW} + V_C^{2/3} \gamma_{CW}$$

After engulfment has occurred (see Fig. 1) we can similarly write,

$$E_{ENG} = 4\pi R_T^2 \gamma_{CH} + 4\pi R_T^2 \gamma_{HW}$$

and

$$E_{ENG}/4\pi(3/4\pi)^{2/3} = V_C^{2/3} \gamma_{CH} + V_T^{2/3} \gamma_{HW} \quad ,$$

where  $R_T$  = the radius of the final particle. It is also assumed that after engulfment the volume of the core particle has not changed. The energy involved is thus:


$$\Delta E = E_{ENG} - E_{SEP}$$

so that provided  $\Delta E$  is negative the process is thermodynamically favourable. Alternatively, the condition for engulfment can be expressed as,

$$V_C^{2/3} \gamma_{CH} + V_T^{2/3} \gamma_{HW} < V_H^{2/3} \gamma_{HW} + V_C^{2/3} \gamma_{CW}$$

Fractional volumes of the particles can also be expressed in the form,

$$\phi_C = V_C/V_T \quad \text{and} \quad \phi_H = V_H/V_T$$

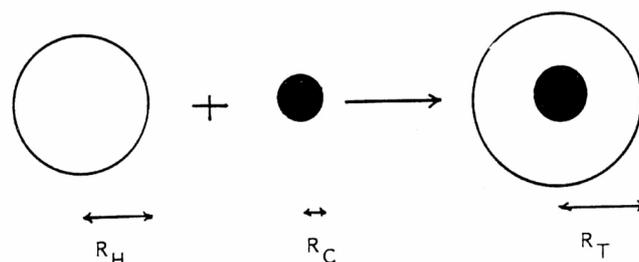

**Fig. 1** Schematic illustration showing the engulfment of a core particle of radius,  $R_C$ , into a host particle of radius,  $R_H$ , to form a composite particle of radius  $R_T$

where,

$$\phi_C + \phi_H = 1$$

In terms of fractional volume it follows from the inequality (1) that,

$$\phi_H^{2/3} \gamma_{HW} + \phi_C^{2/3} \gamma_{CW} > \phi_C^{2/3} \gamma_{CH} + \gamma_{HW}$$

and

$$\frac{\gamma_{CW} - \gamma_{CH}}{\gamma_{HW}} > \frac{1 - \phi_H^{2/3}}{\phi_C^{2/3}}$$

Figure 2 shows a plot of the right-hand side of the inequality (2) as a function of  $\phi_C$ ; this shows the region above the curve where the conditions for engulfment are fulfilled. The left-hand side of the expression (2) can also be written in terms of the contact angle,  $\theta$ , in the form of Young's equation, namely,

$$(\gamma_{CW} - \gamma_{CH})/\gamma_{HW} = \cos \theta$$

Thus complete spreading is achieved when  $\cos \theta = 1.0$ . However, it has been indicated [26-27] that the energy change, from separated to engulfed, can increase with increasing values for the interfacial energy expression to values greater than unity. The value increases with

- i) increasing  $\gamma_{CW}$ , that is with an increased hydrophobic nature of the core particle,
- ii) decreasing  $\gamma_{HW}$ , that is with an increased hydrophilic tendency of the surface of the engulfing particles,
- iii) decreasing  $\gamma_{CH}$ , which occurs if the interior of the engulfing particle becomes more like the surface of the core particle.

Kinetic factors have not been considered in this section, however, it is clear that internal re-arrangement of particle morphology towards the favoured structure may be completely inhibited or very slow in some systems, such as those in which the host polymer is cross-linked or is in the glassy state.



The ratio of PS to PBMA particles in the cluster was controlled by adjusting the particle number concentrations of the two latices prior to mixing. The concentration of the PS latex was chosen arbitrarily to be that needed to cover one-quarter of the surface area of the PBMA particles assuming that complete adsorption occurred. In principle therefore each cluster had a ratio of 68 PS particles to one PBMA particle. During the addition process the electrolyte concentration was maintained at about  $10^{-5}$  moldm<sup>-3</sup> sodium chloride. The mixture was allowed to stand for 24h at room temperature after which it was ultra-sonicated for 30 min to break up any flocs formed as a consequence of particle-particle bridging flocculation.

In order to achieve particle engulfment the mixed dispersion in the sample bottle was placed in an oil bath at 70°C for 24h. This temperature was above the T<sub>g</sub> of PBMA (35°C) and hence allowed the PS particles to become ingested into the PBMA spheres to produce a curant-bun type morphology.

#### Characterisation of the latex particles

##### *Electron microscopy*

For electron microscopy examination dilute samples of the latices were placed on carbon coated copper grids. These were examined at low beam intensities using a JOEL JEM-100CX transmission electron microscope. From the micrographs obtained prints were made and used in conjunction with a Carl Zeiss TGZ 3 particle size analyser to obtain a number-average particle diameter. For each determination about 800 particles were counted.

The particle clusters obtained from the heterocoagulation process were also examined using the same transmission electron microscope, using carbon replicas of the composite particles.

In order to obtain information on the internal particle morphology of the PBMA particles, after engulfment had occurred, thin sections were prepared for examination. Initially, the aqueous composite particle mixture was converted to a dry powder by freeze-drying. The powder was then imbedded in a resin which was prepared from 10ml of Araldite CY212, 10ml of dodecylenyl succinic anhydride and 0.4ml of benzyl dimethylamine; this mixture was left at room temperature for 2 weeks to harden. Thin sections were prepared from the hardened resin using a Sorvall MT-2 ultramicrotome with a freshly prepared glass knife. The thin sections were floated off on to a water reservoir and those of suitable thickness collected on copper grids; the latter were placed on a thin piliform film for

support and protection of the sections. Then, the sections were stained with ruthenium tetroxide to highlight PS relative to PBMA during electron microscope examination. Finally, the sections were carbon coated to provide stability in the electron beam.

##### Disc centrifuge photosedimentometry

A Brookhaven spinning disc centrifuge, type DCP-1000 Particle-Sizer, was also used for the determination of particle size and to obtain an estimate of the size distribution. Water (15cm<sup>3</sup>) was used as the spin fluid and just prior to running 1cm<sup>3</sup> of 50% of a methanol/water (v/v) mixture was added in order to set up a density gradient. 0.2cm<sup>3</sup> of an aqueous latex at an appropriate concentration (ca 1%w/v) to give a peak was injected on to the surface of this in 50% methanol/water. Within the instrument a photodetector was located at a known distance from the centrifuge axis, R<sub>d</sub>, in order to measure turbidity at this position as a function of time, t, from injection of the sample R<sub>i</sub>. This time is directly related to the angular frequency of the disc, ω, the particle diameter, D, the difference between the density of the particle and the fluid, Δρ, and the fluid viscosity, η, by:

$$t = 18\eta \ln[R_d/R_i] / \omega^2 D^2 \Delta\rho .$$

It is clear from this equation that the time taken for a particle to move to the measuring point is inversely proportional to the square of its diameter thus giving good resolution in size. The Brookhaven software provided with the instrument converted the photometric turbidity measurements into a particle size distribution (see later). The density difference parameter, Δρ, is an important parameter in the equation and hence the densities of all the particles and the spin fluid were determined using an Anton Paar density meter.

##### Electrophoresis


In order to determine the sign of the electric charge on the particles and the magnitude of the zeta-potential as a function of pH, electrophoretic measurements were made on the particles of each latex. The PS latex which contained small particles was examined using a Malvern Zeta-sizer II. The PBMA latex particles were examined using a moving boundary technique in the manner previously described (31). The compound particles were examined using a Pen Kem, system 3000, electrokinetic analyser. All the measurements were made in a salt concentration of 10<sup>-3</sup> moldm<sup>-3</sup>.

## Results

### Electron microscopy

Figure 3 shows transmission electron micrographs of the particles of PBMA, which were used as the host particles, and particles of PS which were used for engulfment into the host particles to form core particles. As can be seen both sets of particles were fairly monodisperse; particle size data obtained from electron microscopy is given in Table 1.


Some electron micrographs of carbon replicas of heterocoagulated units formed by mixing the small PS particles

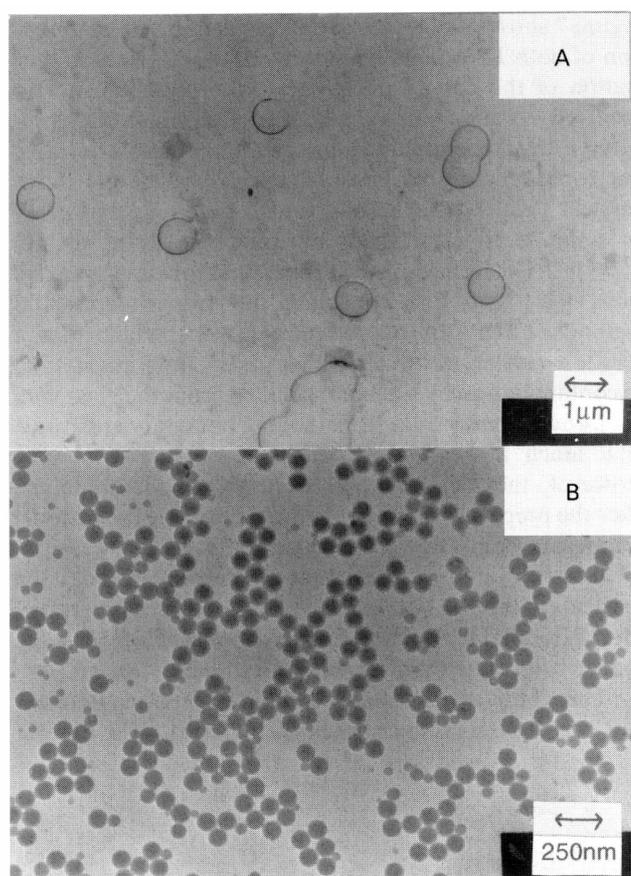

**Fig. 3** Electron micrographs of **A** PBMA particles and **B** PS particles

with the large PBMA particles are shown in Fig. 4. The micrographs which were taken on samples following ultrasonication but prior to heat treatment indicate that some partial engulfment already seems to have occurred.

Figure 5 shows electron micrographs of sections cut from particles which had been taken up to a temperature of 70°C, that is well above the T<sub>g</sub> of PBMA. As can be seen engulfment has occurred and the PS particles are clearly visible in the PBMA host particles. It appears from the micrographs that some change in the PS particles has occurred during the engulfment and, as anticipated, that

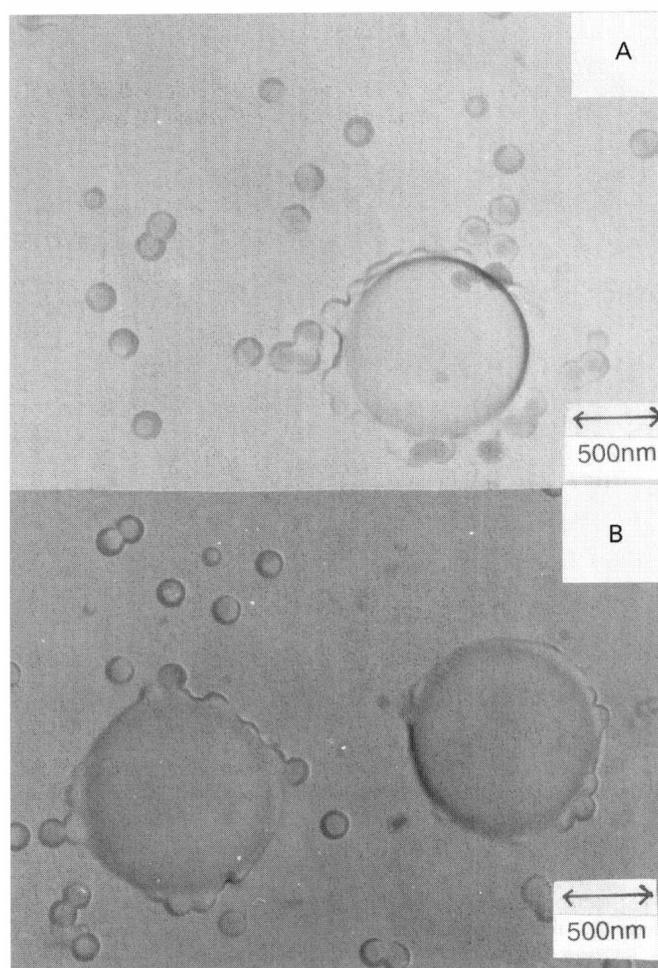


**Fig. 4** Electron micrographs of carbon replicas of PS and PBMA particles following the heterocoagulation process

Table 1 Particle-particle engulfment

Particle	Polymer	Radius/nm	Coef. Var. %	T <sub>g</sub> /°C	Stabilisation mechanism
Host	PBMA	446 <sup>†</sup>	2.9	35	Electrosteric/Cationic
Core	PS	45 <sup>†</sup>	28.8	106	Electrostatic/Anionic


<sup>†</sup> Transmission electron microscopy, number average.

more than one PS particle per PBMA particle has been engulfed. Moreover, in places partial exposure of the PS surface appears to occur which suggests that for some particles the engulfment is incomplete; this feature is also illustrated in Fig. 6.

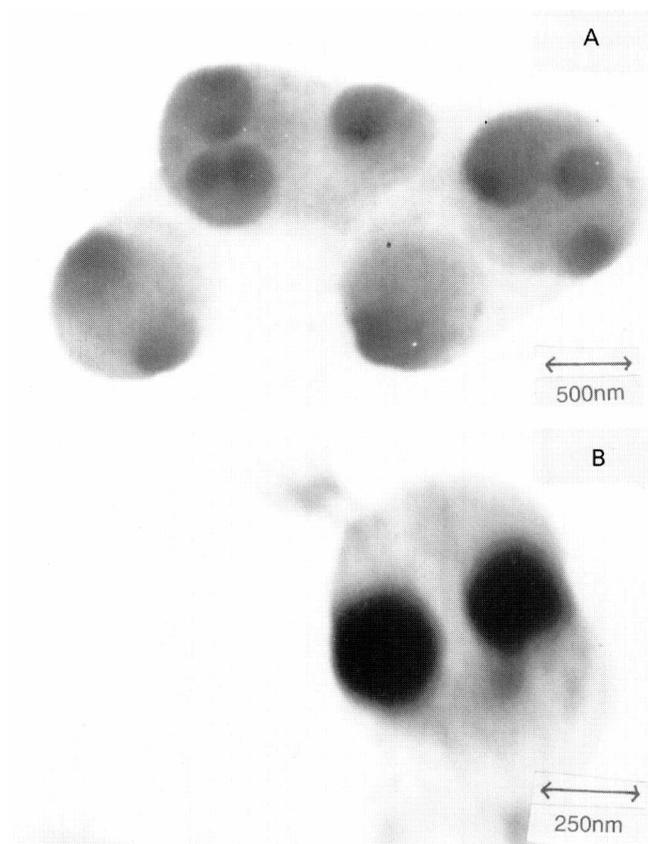

**Fig. 5** Electron micrographs of sections cut from composite particles after the heterocoagulated particles had been raised 35°C above the Tg of the PBMA particles

**Fig. 6** Electron micrographs of sections cut from composite particles after the heterocoagulated particles had been raised 35°C above the Tg of the PBMA particles to illustrate examples of particle engulfment

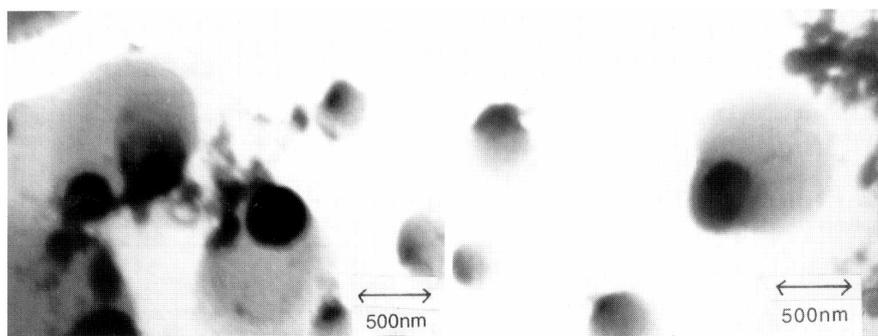


An additional feature of Fig. 5 is that the engulfed PS particles appear to be larger than the size of the original PS particles. One possibility is that the PS particles do not retain colloid stability within the host particle and hence flocculate. Thus if the PS particles join together this reduces the area exposed to the PBMA and hence reduces the interparticle interfacial energy which makes this a favourable process. It is also possible that some smearing of the PS particles could have occurred during microtome sectioning although this was carried out well below the Tg of PS.

#### Electrophoresis studies

Figure 7 shows the results of electrophoresis examination of both PS and PBMA particles as well as an examination of the composite particles after engulfment had occurred. As anticipated the PS particles, which were prepared using a persulphate initiator, maintained a negative electrophoretic mobility over the whole of the pH range studied. The PBMA particles, which were prepared using an amidine initiator, had an isoelectric point at pH  $4.2 \pm 0.1$ . This value was lower than that found in previous work [32] but was confirmed by two experimental methods. Firstly, by microelectrophoresis, which uses a very low concentration of particles and can be susceptible to contamination by siliceous anions from the glassware [33], and secondly by using a moving boundary apparatus at a much higher concentration latex (10.0% w/v). However, the measurements were also made sometime after the preparation and as shown previously the cationic charge can decay slowly with time [32].

It should also be noted that in the present work the surface of the PBMA particle had chemically grafted MeOPEG chains on the surface which would influence the charge behaviour by displacing the surface of shear.

The composite particles examined after engulfment had occurred also had negative mobility over the pH

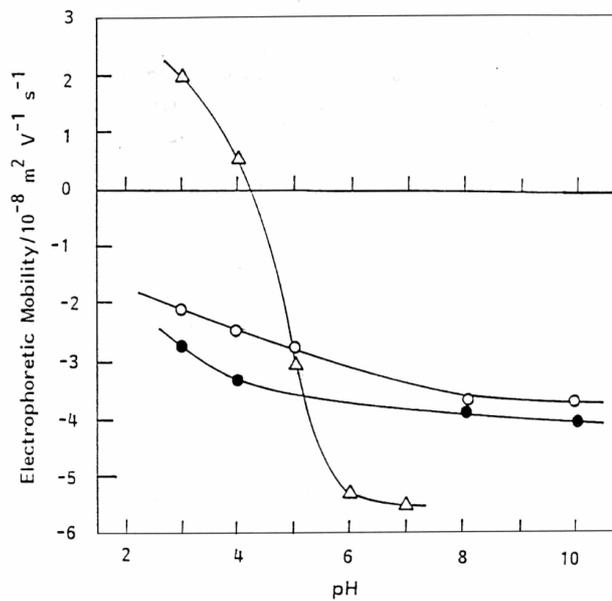

**Fig. 7** Electrophoresis mobility against pH for:  $\triangle$ , PBMA particles;  $\bullet$ , PS particles;  $\circ$ , composite particles. Salt concentration  $10^{-3} \text{ mol dm}^{-3}$  sodium chloride


range examined. This was unexpected since it was anticipated that engulfment of the PS particles would give the composite particles electrophoresis characteristics resembling those of the PBMA particles. In fact, the results resembled more closely those of the PS particles. This could be a consequence of the fact that not all the PS particles were completely engulfed and that some PS surface still remained exposed to the external aqueous phase. This view is to some extent supported by the electron micrographs of thin sections shown in Figs. 5 and 6.

#### Heterocoagulation

Since the electrophoresis studies indicated that the electrosterically stabilised PBMA particles were only positively charged below pH 4.2 mixing of the PS and PBMA particles was carried out below this value. As shown in the electron micrographs of Fig. 4 it is clear that heterocoagulation occurred under these conditions although, as anticipated, complete coverage of the surface of the PBMA particles did not occur.

#### Disc centrifuge experiments

Figures 8A and 8B show the traces obtained from the disc centrifuge experiments. The trace for the PBMA latex

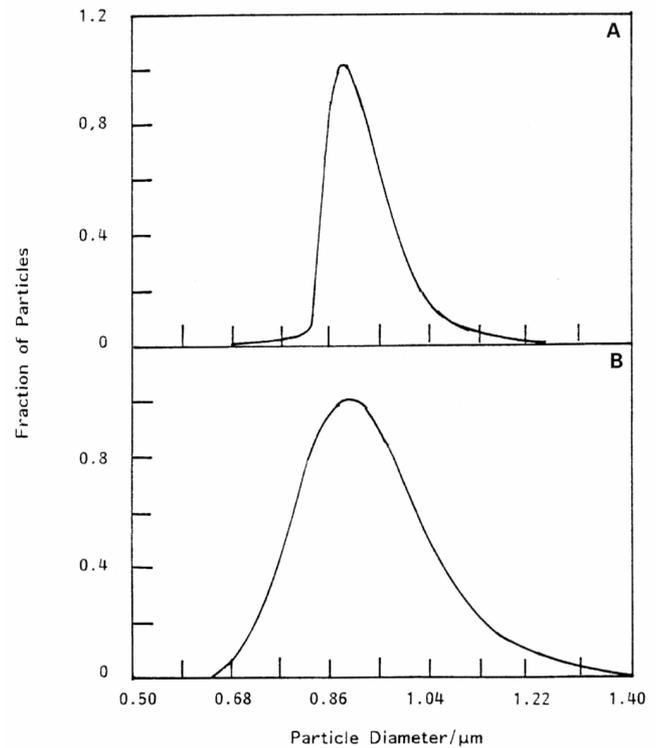

**Fig. 8** Traces obtained by disc centrifuge photosedimentometry for **A** PBMA particles **B** composite particles after the engulfment process

indicates a rather narrow size distribution with the mode of the curve at 885nm; the weight average diameter was found to be 926nm. The trace for the particles after the engulfment process was significantly broader and the mode of the curve had moved to 889nm; the weight average diameter was found to be 938nm. The shape of the traces suggests that a significant change has occurred in the size distribution of the PBMA particles after engulfment has occurred to form composite particles. In addition, a question arises to whether a density distribution is generated within the composite particles as a consequence of the variation in the number of PS particles taken up by each PBMA particle. As mentioned earlier the density of the particles affects the  $\Delta\rho$  term in Eq. (3) and thus the analysis of the results.

#### Discussion

Figure 9 illustrates schematically the basic objective of the present work which was to engulf one set of polymer colloid particles of high Tg into a host particle of lower Tg. The first stage of the process involved the synthesis of particles with appropriate size and bulk and surface

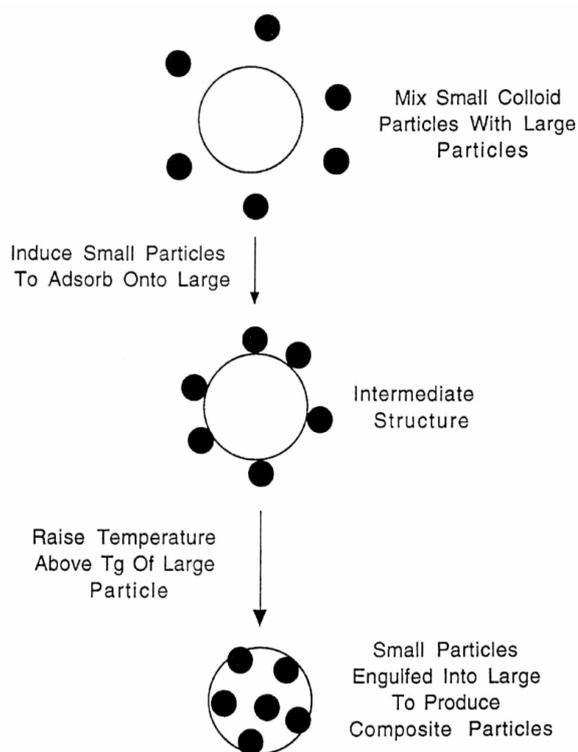


Fig. 9 Schematic flow chart of the process of particle engulfment

properties. PS particles of diameter 45nm and a  $T_g$  of ca 106°C were prepared using emulsifier-free polymerisation and a persulphate initiator. The host PBMA particles, diameter 446nm and  $T_g$  35°C were prepared using emulsifier-free polymerisation and ABA.2HCL as initiator; towards the end of the polymerisation MeOPEGMA was added to provide grafted MeOPEG chains on the surface and hence electrosterically stabilised particles.

The second stage involved mixing cationic PBMA particles with the anionic PS particles under favourable conditions for heterocoagulation in order to obtain a coating of the small particles on the larger host particles.

Finally at the third stage the mixed system was heated to 70°C for 24h, a temperature 35°C above the  $T_g$  of the PBMA.

As demonstrated in the previous section this scheme successfully produced composite particles of PS engulfed in PBMA. The final particle exhibited properties associated with electrosteric stabilisation, as for example exemplified by their good freeze-thaw properties, indicating that the MeOPEG chains remained on the surface of the composite particles following the engulfment process.

In the theoretical section of this presentation and in previous papers [23-26] a thermodynamic argument was proposed that if the surface energies of the host and core particles were correctly chosen then logically engulfment of the core by the host would occur, namely provided that

the magnitude of  $(\gamma_{CW} - \gamma_{HW})/\gamma_{HW}$  was greater than one. Further theoretical development [27] indicated that a structure in which the core particles was only partially engulfed by the host would be favoured if  $-1 < (\gamma_{CW} - \gamma_{CH})/\gamma_{HW} < 1$ . The lower energy of the final state is a compelling reason for the thermodynamic transition and the success of the experiments carried out provide strong evidence in favour of the importance of the thermodynamic process. However, a complete test of the hypothesis involves a precise knowledge of the surface energies of the particles involved and at the present time data of sufficient precision is not available. Although a number of attempts have been made to obtain information for polymer surfaces [34, 35] the results have been qualitative rather than quantitative. In addition, neither the influence of surface charge nor the influence of MeOPEG chains has been assessed precisely. In principal, both of these should decrease the surface energy and these factors may well have facilitated engulfment by aiding the condition that  $(\gamma_{CW} - \gamma_{CH})/\gamma_{HW}$  should be less than unity.

An additional question that must be considered is to what extent factors other than thermodynamic might influence the engulfment process. Although thermodynamic factors may supply the main motivation kinetic factors are also important since the process of a core particle passing into the host particle must, of necessity, involve hydrodynamic flow of the host polymer in order to allow passage of the incoming particle. Thus it is unlikely that this process could occur if the host particle was in the glassy state or cross-linked. For this reason PBMA was chosen as the polymer for the host particle since it has a low  $T_g$  and in order to achieve engulfment the temperature of the heterocoagulated units could be raised 35°C above the  $T_g$  of PBMA. At this temperature engulfment was successful but using temperature as a variable was not examined in detail.

Although the present study has been confined to polymer colloid particles the principles should be more generally applicable. Other experiments have shown that a number of inorganic particles such as magnetite can be engulfed into a polymeric host particle by this process [36].

It is also of interest that some years ago surface energy arguments were used by Mudd et al [37] to explain the process of phagocytosis, that is engulfment of biologically alien particles by polymorphonuclear leucocytes.

**Acknowledgements** We wish to express our thanks to ICI Paints Division for support of the work from the Strategic Research Fund. We also thank Drs S. Downing and N. Williams for a number of useful discussions.

## References

1. Daniel JC (1985) *Makromol Chem Suppl* 10/11:359
2. Vanderhoff JW, Dimonie V, El-Aasser MS, Klein E (1985) *Makromol Chem Suppl* 10/11:391
3. Sutterlin N (1985) *Makromol Chem Suppl* 10/11:403
4. Lee DI, Ishikawa T (1983) *J Pol Sci Pol Chem Ed* 21:143
5. Cho I, Lee DI (1985) *J Appl Pol Sci* 30:1903
6. Okubo M, Ando M, Yamada A, Katsuta Y, Matsumoto TJ (1981) *J Pol Sci Lett Ed* 19:143
7. Bootle GA, Lye JE, Ottewill RH (1990) *Makromol Chem Makromol Symp* 35/36:291
8. Okubo M (1990) *Makromol Chem Makromol Symp* 35/36:307
9. Okubo M, Yamada A, Matsumoto A (1990) *J Pol Sci Pol Chem Ed* 22:3219
10. Jonsson JEL, Hassander H, Jansson LH, Tornell (1991) *Macromolecules* 24:126
11. Lee S, Rudin A (1992) *Acs Symposium Series* 492:234
12. Vandezande GA, Rudin A (1992) *ACS Symposium Series* 492:119
13. Chen YC, Dimonie V, El-Aasser MS (1992) *J Appl Polymer Sci* 45:487
14. Vandezande GA, Rudin A (1992) *ACS Symposium Series* 492:119
15. Okubo M, Miyachi N, Lu Y (1994) *Colloid Polym Sci* 272:270
16. Fitch RM (1995) *Makromol Symp* 92:1
17. Rudin A (1995) *Makromol Symp* 92:53
18. Ottewill RH, Cole SJ, Waters JA (1995) *Makromol Symp* 92:97
19. Berg J, Sundberg DC, Kronberg B (1986) *Polym Mater Sci Eng* 54:367
20. Berg J, Sundberg DC, Kronberg B (1989) *J Microencapsulation* 6:327
21. Sundberg DC, Cassassa AP, Pantazopoulos J, Muscato MR (1990) *J Appl Polymer Sci* 40:1425
22. Sundberg DC, Durant YG (1995) *Makromol Symp* 92:43
23. Waters JA (1990) US Patent 5210113
24. Water JA (1993) European Patent 0327199
25. Water JA (1993) US Patent 5296524
26. Water JA (1994) *Colloids and Surfaces* 83:167
27. Water JA (1995) In: Goodwin JW, Bus-Call R (eds) *Colloidal Polymer Particles*, Academic Press, London
28. Ottewill RH, Satgurunathan R, Westby MJ (1987) *Br Polm J* 19:435
29. Ottewill RH, Satgurunathan R (1987) *Colloid Polym Sci* 265:845
30. Goodwin J, Hearn J, Ho CC, Ottewill RH (1974) *Colloid Polym Sci* 252:464
31. Ottewill RH, Shaw JN (1967) *Kolloid Z u Z Polymere* 218:34
32. Goodwin JW, Ottewill RH, Pelton R (1979) *Colloid Polym Sci* 257:61
33. Ottewill RH, Woodbridge RF (1964) *J Colloid Sci* 19:606
34. Wu S (1982) *Polymer Interface and Adhesion*, Marcel Dekker, New York
35. Cole SJ (1992) PhD Thesis, University of Bristol
36. Schofield AB (1995) to be published
37. Mudd S, McCutcheon M, Lucke B (1934) *Physiol Rev* 14:210